

ACEROS PARA TRABAJO EN FRÍO

Segmentos de aplicación

Trabajo en frío

Formatos disponibles

Productos largos*

Chapas

* Los datos presentados se refieren exclusivamente a productos largos. Consulte las explicaciones detalladas al final de la ficha técnica (pdf).

Descripción

K353 es un acero universal de herramientas para aplicaciones de trabajo en frío.

Excepcional por su alta dureza, alta resistencia al desgaste y extraordinaria tenacidad.

K353 es un acero con 8 % de cromo producido convencionalmente, con buena maquinabilidad, tenacidad y estabilidad dimensional.

Método de obtención

Aire fundido

Propiedades

> Estabilidad dimensional : buena

Aplicaciones

- > Cuchillas de máquinas (fabricantes)
- > Conformado en frío
- > Corte fino / Troquelado / Estampado
- > Temple en prensa / Estampación en caliente
- > Sistemas de canal caliente

Composición Química

C	Si	Mn	Cr	Mo	V	Al
0,82	0,70	0,40	8,00	1,60	0,60	+

Características

	Resistencia a la compresión	Estabilidad dimensional durante el tratamiento térmico	Tenacidad	Resistencia al desgaste abrasivo	Resistencia al desgaste adhesivo
BÖHLER K353	★★	★★★	★★	★★	★★
BÖHLER K100	★★	★★	★	★★★	★★
BÖHLER K105	★★	★★	★	★★	★★
BÖHLER K107	★★	★★	★	★★★	★★
BÖHLER K110	★★	★★★	★	★★★	★★
BÖHLER K190 MICROCLEAN	★★★★	★★★★★	★★★★	★★★★	★★★★
BÖHLER K294 MICROCLEAN	★★★★★	★★★★★	★★★★	★★★★★	★★★★★
BÖHLER K340 ECOSTAR	★★★	★★★	★★	★★	★★
BÖHLER K340 ISODUR	★★★	★★★★	★★★	★★★	★★★★
BÖHLER K346	★★★	★★★	★★★	★★★★	★★
BÖHLER K360 ISODUR	★★★	★★★★	★★★	★★★★	★★★★
BÖHLER K390 MICROCLEAN	★★★★★	★★★★★	★★★★	★★★★★	★★★★★
BÖHLER K490 MICROCLEAN	★★★★	★★★★★	★★★★	★★★★	★★★★
BÖHLER K497 MICROCLEAN	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K888 MATRIX	★★★★	★★★★★	★★★★★	★★	★★
BÖHLER K890 MICROCLEAN	★★★★	★★★★★	★★★★★	★★★	★★★

Estado de suministro

Recocido

Dureza (HB)	máx. 240
-------------	----------

Tratamiento térmico

Recocido

Temperatura	800 a 850 °C	Slow controlled cooling in furnace at a rate of 10 to 20 °C/hr (18 to 36 °F/hr) down to approximately 600 °C (1112 °F) Further cooling in air.
-------------	--------------	---


Alivio del estrés

Temperatura	650 °C	After through heating, hold in neutral atmosphere for 1-2 hours. Slow cooling in furnace Intended to relieve stresses caused by extensive machining or in complex shapes.
-------------	--------	---

Temple y revenido

Temperatura	1.030 a 1.060 °C	Quenching: Oil, salt bath, gas. Holding time after temperature equalization: 15 to 30 minutes. After hardening, tempering to the desired working hardness according to the tempering chart.
-------------	------------------	---

Tempering chart

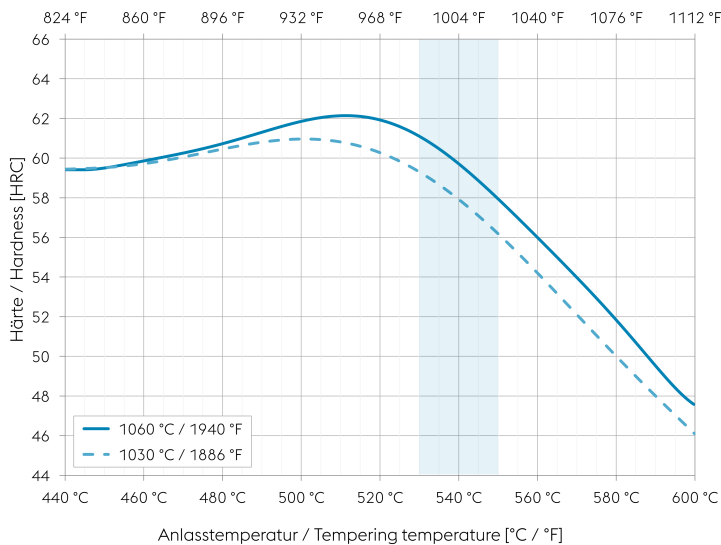

Specimen size: square 20 mm (0,787 inch)

Slow heating to tempering temperature immediately after hardening.

Time in furnace 1 hour for each 20 mm (0,787 inch) of workpiece thickness but at least 2 hours.

Please refer to the tempering chart for guide values for the achievable hardness after tempering.


It is recommended to temper at least three times above the secondary hardness maximum.

Cooling in air to room temperature after each tempering step is recommended.

Tempering for stress relieving 30 to 50 °C (86 to 122 °F) below the highest tempering temperature.

Recommended tempering temperature range is indicated by the blue area in the chart.

Continuous cooling CCT curves

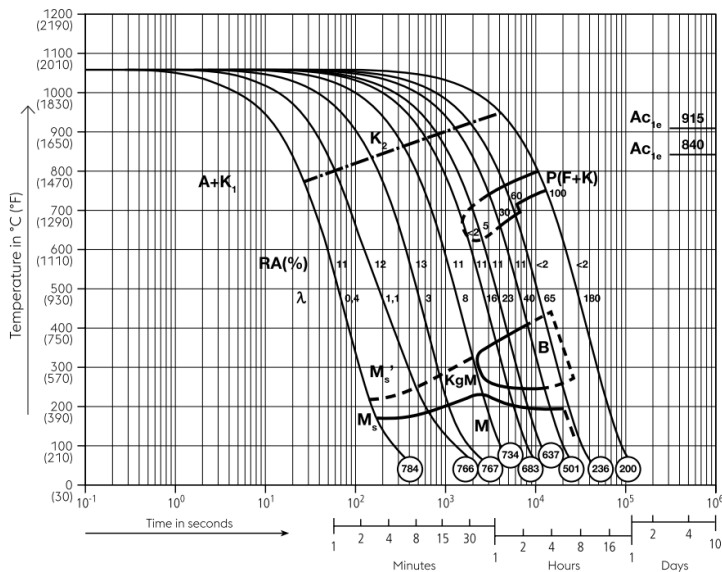

Austenitising temperature: 1060 °C (1940 °F)
Holding time: 30 minutes


O Vickers hardness

2...100 phase percentages

0.3...180 cooling parameter λ , i.e. duration of cooling from 800 to 500 °C (1472 to 932 °F) in $s \times 10^{-2}$

A... Austenite
K... Carbide
RA... Retained austenite
P... Pearlite
B... Bainite
M... Martensite
Ms... Martensite starting temperature


Quantitative phase diagram

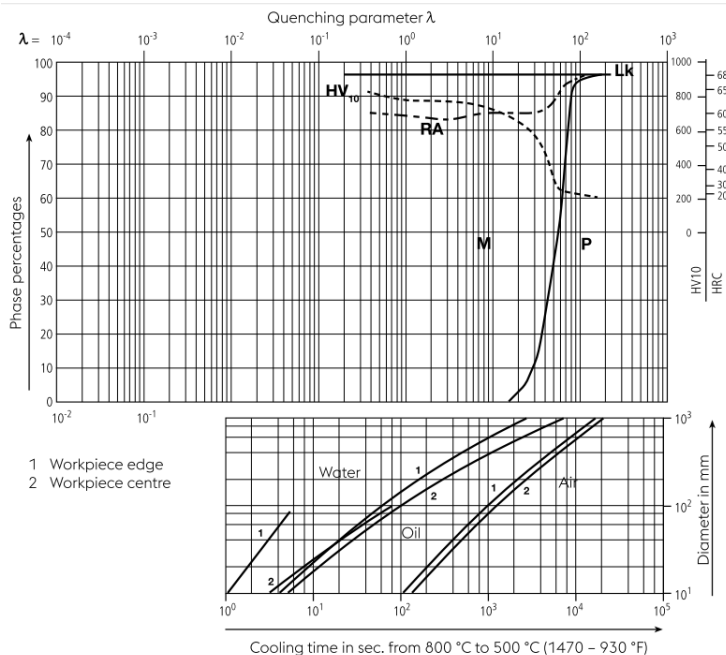

O Vickers hardness
LK... Ledeburitic carbides
RA... Retained austenite
M... Martensite
P... Pearlite

1... Edge or face
2... Core

Heat treatment sequence

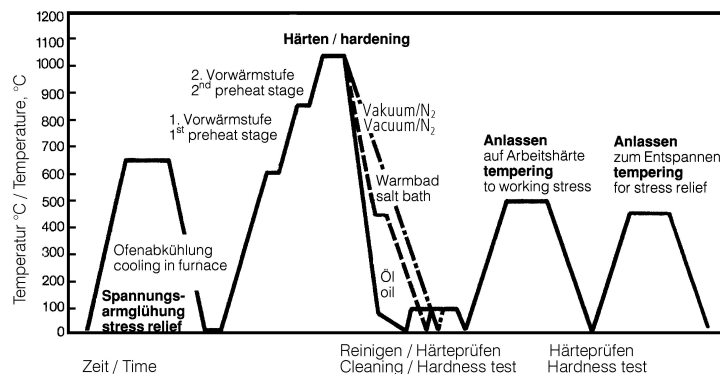

Propiedades físicas

Temperatura (°C)	20
Densidad (kg/dm ³)	7,7
Conductividad térmica (W/(m.K))	21,9
Calor específico (kJ/kg K)	0,47
Resistencia eléctrica específica (Ohm.mm ² /m)	-
Módulo de elasticidad (10 ³ N/mm ²)	212

Expansión térmica

Temperatura (°C)	100	200	300	400	500
Expansión térmica (10^{-6} m/(m.K))	11	11,3	11,6	12	12,4

Los datos de este folleto no son vinculantes y no se consideran una promesa, sino que sólo sirven como información general. Esta información sólo es vinculante si se establece expresamente como condición en un contrato celebrado con nosotros. Los datos medidos son valores de laboratorio y pueden desviarse de los análisis prácticos. En la fabricación de nuestros productos no se utilizan sustancias perjudiciales para la salud o la capa de ozono.