

HIGH SPEED STEELS

Available Product Variants

Long Products*

Plates

*) Presented data refer exclusively to long products. Please observe the detailed explanations at the end of the data sheet (pdf).

Product Description

BÖHLER S390 MICROCLEAN – "The decathlete"

This grade is our PM steel with many positive usage properties. For twist drills, taps, mills, broaches, or cold-work applications, BÖHLER S390 MICROCLEAN is always a high performer.

Process Melting

Powder metallurgy

Properties

- > Toughness & Ductility : high
- > Wear Resistance : high
- > Compressive strength : very high
- > Edge Stability : very high
- > Grindability : high
- > Hot Hardness (red hardness) : very high

Applications

- > Automotive Racing
- > End Mills
- > Powder Pressing
- > Special Cutting Tools
- > Pill punching dies
- > Broaches and Reamers
- > Fine Blanking, Stamping, Blanking
- > Rolling
- > Twist Drills and Taps
- > Cold Forming / Coining
- > Gear Cutting, Shaving and Shaping Tools
- > Shearing / Machine Knives
- > Wear parts

Chemical composition (wt. %)

C	Cr	Mo	V	W	Co
1.64	4.80	2.00	4.80	10.40	8.00

Material characteristics

	Compressive strength	Grindability	Red hardness	Toughness	Wear resistance	Edge Stability
BÖHLER S390 MICROCLEAN®	★★★★	★★★	★★★★	★★★★	★★★★	★★★★
BÖHLER S290 MICROCLEAN®	★★★★★	★	★★★★	★★	★★★★★	★★★★
BÖHLER S393 MICROCLEAN®	★★★★	★★★	★★★★	★★★★	★★★★	★★★★
BÖHLER S590 MICROCLEAN®	★★★★	★★★	★★★★	★★★	★★★	★★★
BÖHLER S592 MICROCLEAN®	★★★★	★★★	★★★★	★★★	★★★	★★★
BÖHLER S690 MICROCLEAN®	★★★	★★★	★★	★★★★★	★★★	★★
BÖHLER S692 MICROCLEAN®	★★★	★★★	★★	★★★★★	★★★	★★
BÖHLER S790 MICROCLEAN®	★★★	★★★	★★	★★★★	★★	★★★
BÖHLER S792 MICROCLEAN®	★★★	★★★	★★	★★★★	★★	★★★
BÖHLER S793 MICROCLEAN®	★★★	★★★	★★★★	★★★	★★★	★★★

Delivery condition

Annealed	
Hardness (HB)	max. 320 drawn execution max. 320 HB
Tensile Strength (MPa ksi)	max. 1,080 157
Hardened and Tempered	
Hardness (HRC)	64 to 68

Heat treatment


Annealing		
Temperature	770 to 840 °C 1,418 to 1,544 °F	4 h controlled slow cooling in furnace (10 to 20°C/h / (50 to 68°F/h) to 740°C/2h (1364°F/2 h) cooling in furnace,
Stress relieving		
Temperature	600 to 650 °C 1,112 to 1,202 °F	Slow cooling in furnace. To relieve stresses set up by extensive machining or in tools of intricate shape. After through heating, hold in neutral atmosphere for 1 to 2 hours.
Hardening and Tempering		
Temperature	1,100 to 1,230 °C 2,012 to 2,246 °F	Salt bath, vacuum Preheating: 1st stage ~ 500 °C (930 °F), 2nd stage ~ 850 °C (1560 °F), 3rd stage ~1050 °C (1920 °F) Austenitising: 1100 - 1230 °C (2012 °F - 2246 °F), holding time after complete heating 80 seconds, maximum 150 seconds, to avoid material damage due to overheating. Quenching: oil, warm bath (500 - 550 °C (930 °F - 1020 °F)), gas
Temperature	550 to 570 °C 1,022 to 1,058 °F	Slow heating to tempering temperature immediately after austenitising. Holding time in the furnace 1 hour per 20 mm material thickness (at least 1 hour) Slow cooling to room temperature between each tempering step 3 tempering cycles recommended Hardness see tempering chart

Continuous cooling CCT curves

Austenitising temperature: 1230°C
Haltedauer: 180 Sekunden

Austenitising temperature: 1230°C (2246°F)
Holding time: 180 seconds

Austenitising temperature: 1230°C (2246°F)
Holding time: 180 seconds

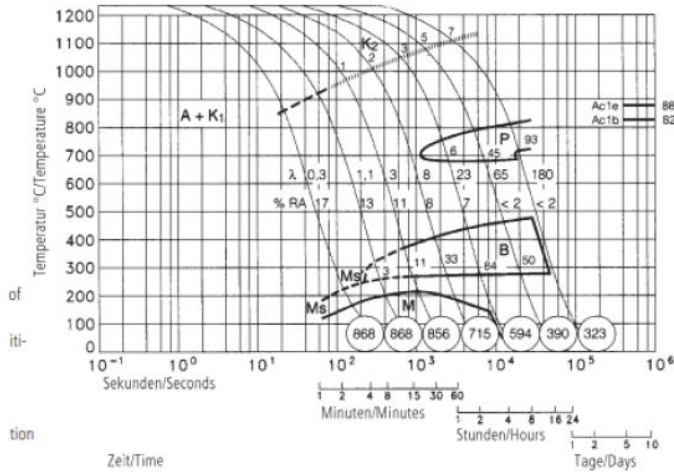


A....Austenite
B....Bainite
K....Carbide
P....Pearlite
M....Martensite
RA...Retained Austenite

Quantitative phase diagram

Austenitising temperature: 1230°C
Haltedauer: 180 Sekunden

Austenitising temperature: 1230°C (2246°F)
Holding time: 180 seconds

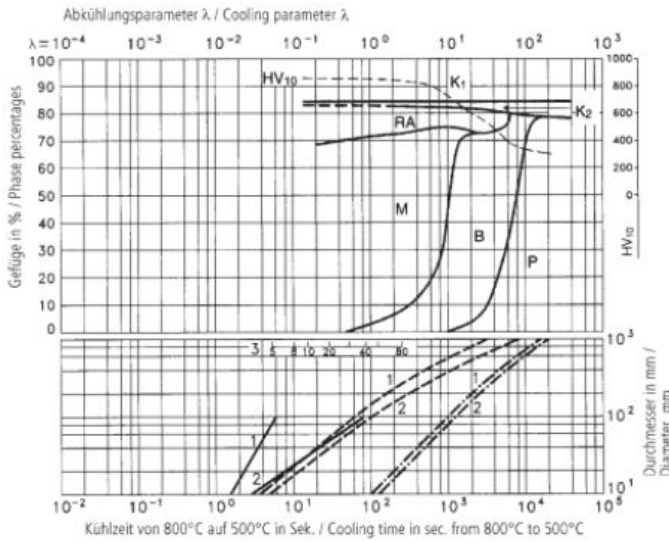


A....Austenite
B....Bainite
K....Carbide
P....Pearlite
M....Martensite
RA...Retained Austenite

1....Edge or Face
2....Core
3....Jominy test: distance from quenched end

— watercooling
- - oilcooling
- · - aircooling

Tempering Chart

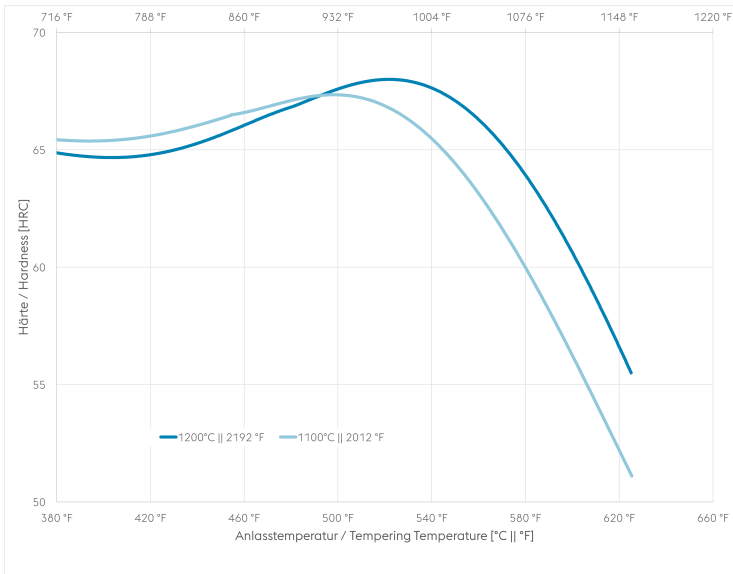

Holdingtime 3x2 hours

Specimensize: square 25mm

Austenitising in vacuum

Physical Properties

Temperature (°C °F)	20 68
Density (kg/dm ³ lb/in ³)	8.1 0.29
Thermal conductivity (W/(m.K) BTU/ft h °F)	17 9.82
Specific heat (kJ/kg K BTU/lb °F)	0.42 0.1003
Spec. electrical resistance (Ohm.mm ² /m 10 ⁻⁴ Ohm.inch ² /ft)	0.61 2.88
Modulus of elasticity (10 ³ N/mm ² 10 ³ ksi)	231 33.5

Thermal Expansions between 20°C | 68°F and ...

Temperature (°C °F)	100 212	200 392	300 572	400 752	500 932	600 1,112	700 1,292
Thermal expansion (10 ⁻⁶ m/(m.K) 10 ⁻⁶ inch/inch.°F)	10 5.6	10.5 5.8	10.8 6	11.2 6.2	11.3 6.3	11.4 6.3	11.6 6.4

Long Products: For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

Sheet & Plates: Product Variant may differ in terms of melting process, technical data, delivery, and surface condition as well as available product dimensions. Please contact voestalpine BÖHLER Bleche GmbH & Co KG.

The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.